



Engineered hydrochar production methodologies, key factors influencing agriculture wastewater treatment, and life cycle analysis: A critical review

Oscar M. Rodriguez-Narvaez^{a,*}, Kannan Nadarajah^b, V.A. Suarez-Toriello^c, Erick R. Bandala^d, Ashantha Goonetilleke^e

^a CIATEC, A.C., Centro de Innovación Aplicada en Tecnologías Competitivas, Omega 201, Col. Industrial Delta, 37545 León, GTO, Mexico

^b Department of Agricultural Engineering, Faculty of Agriculture, University of Jaffna, Sri Lanka

^c CONACYT-UAM, Universidad Autónoma Metropolitana-Iztapalapa, Área de Ingeniería Química, Av. FFCC R. Atlixco 186, 09340 Iztapalapa, CDMX, Mexico

^d Division of Hydrologic Sciences, Desert Research Institute, 755 E. Flamingo Road, 89119 Las Vegas, NV, USA

^e School of Civil and Environmental Engineering, Queensland University of Technology (QUT), 2 George Street, Brisbane 4001, Queensland, Australia

ARTICLE INFO

Keywords:

Carbon-based materials
Hydrochar
Synthesis
Pollutant adsorption
Water treatment
Life cycle analysis

ABSTRACT

For intensive food production, a range of chemical compounds are used to increase production, reduce the amount of weeds, and prevent pest infestation. Therefore, agricultural wastewater discharge to water bodies creates human health and environmental risks. This highlights the need for technologies to remove organic and inorganic pollutants, where adsorption using carbon-based materials has emerged as a cost-effective and promising alternative for agricultural wastewater treatment with high removal efficacy and alignment with the circular economy concept by generating value-added products, achieving energy conservation and reducing the environmental footprint. Among the different adsorbent materials, hydrochar (HC) has attracted attention because, compared to the thermal processes used for synthesizing other carbon-based materials, it requires relatively milder production conditions and possesses higher adsorption capability for water pollutants. Although HC holds advantages for the adsorption of water pollutants, HC modification using different methods has been found to improve the properties, including adsorption capacity. Accordingly, engineered hydrochar (EHC) has attracted research attention. However, past research publications show that the investigations have focused on material characterization and removal rates, with little knowledge created of the environmental impacts of HC production, application, and disposal. This study reviews current knowledge on EHC synthesis, characteristics, water treatment applications, and life cycle analysis. Initially, production methodologies were investigated to understand their influence on key surface physical and chemical characteristics. This was followed by assessing EHC efficacy for water and wastewater treatment. Finally, the environmental footprint of EHC production, application, and disposal was evaluated to identify critical knowledge gaps and to provide recommendations for future research.

1. Introduction

Agricultural production is relevant to the current water crisis because of significant freshwater consumption [1] and the resulting wastewater containing diverse organic and inorganic pollutants [2–6]. Developing effective agricultural wastewater treatment technologies, therefore, meets a significant need to ensure water security [5,7,8]. Different agricultural wastewater treatment technologies have been proposed, among which adsorption using engineered materials has gained interest because of its low cost and ease of use [2,9–12]. Despite

high pollutant removal efficiency, some adsorbent materials (e.g., carbon nanotubes) possess a significant environmental footprint generating concerns about their sustainable full-scale production and application [13–18]. To avoid these undesirable indirect consequences, adsorbent production should be aligned with the circular economy concept, creating value-added products, extending the life cycle for achieving energy conservation and reducing the environmental footprint in line with Sustainable Development Goal 6 (SDG6) (clean water and sanitation) and other SDGs related to sustainable and clean production, and waste valorization [19–22].

* Corresponding author.

E-mail address: orodriguez@ciatec.mx (O.M. Rodriguez-Narvaez).

<https://doi.org/10.1016/j.jwpe.2023.104483>

Received 19 July 2023; Received in revised form 23 October 2023; Accepted 24 October 2023

Available online 27 October 2023

2214-7144/© 2023 Elsevier Ltd. All rights reserved.

Some carbon-based materials (CBMs) have gained attention because their production is based on using waste biomass as feedstock, requires relatively mild production conditions [19,23–26], and generates key properties which play major roles influencing their effectiveness in environmental applications [27–31]. Hydrochar (HC) is a CBM produced using hydrothermal carbonization (HTC) that requires mild temperature conditions (180–250 °C) compared to other thermal processes used for CBM production [32–34]. HC is reported to have the ability to adsorb organic and inorganic contaminants. This suggests its high potential for use as an adsorbent [35–37]. Compared with other CBMs, HC possesses relatively low porosity and specific surface area, showing seemingly lower pollutant adsorption rates [38,39]. However, HC can be activated/modified [40] to improve its properties for different applications (e.g. water treatment, carbon capture, catalysis, and energy storage) [19,41]. The activated/modified HC, usually termed engineered HC (EHC), has been found to hold advantages for the adsorption of water pollutants. Most past studies which have focused on EHC have been devoted mainly to material characterization and pollutant adsorption rates with little information available on the environmental impacts and life cycle of production/application [42].

In this study, state-of-the-art methodologies for EHC production were investigated to assess its environmental footprint and its fit to the circular economy concept. The key physical and chemical characteristics of EHCs were evaluated to assess their effectiveness for agricultural wastewater treatment applications. Further, the life cycle analysis (LCA) of different EHCs was investigated to understand the current state of knowledge, identify critical knowledge gaps, and provide recommendations for future research.

2. HC production processes

HC is generated from biomass using HTC in the 180–300 °C temperature range and autogenous pressure (2–16 MPa) [43,44]. Cellulose or hemicellulose-related biomass is the most commonly reported feedstock. HTC has been suggested to break down biomass through polysaccharide hydrolysis into smaller oligosaccharides and monosaccharides (e.g., glucose and xylose) [45]. Subcritical water conditions in HTC convert monosaccharides into intermediate organic

compounds through isomerization, dehydration, fragmentation, and condensation reactions (Fig. 1). Glucose and xylose isomerization reactions produce fructose and lyxose [46], while its decomposition leads to organic acids (e.g., acetic, lactic, propionic, levulinic, and formic). Glucose dehydration leads to furfural-related structures which decompose in aldehydes, phenols, and carboxylic acids [47]. Aldol condensation and intermolecular dehydration produce furfural condensation and polymerization [47] and, subsequently, HC [48–50] with combined polyaromatic/polyfuran structure [51].

The influence of feedstock composition on HC chemical and physical characteristics has been explained using HTC biomass transformation pathways [52] [20,53,54]. For example, the production of homogeneous HC from solid waste, a freely available and low-cost feedstock has been identified as having significant drawbacks related to the presence of biomass with mixed long- and short-chain organic structures [19,20]. To produce homogenous HC, biological biomass reduction has been suggested [55–57]. Nevertheless, only a few studies have focused on understanding the role of feedstock chemical and physical properties on HC characteristics, which constitutes a significant knowledge gap that merits further attention. This is because an in-depth understanding of the influence of feedstock on HC characteristics will allow the selection of the most suitable biomass for a specific application and for identifying feedstock modifications to optimize HC performance.

3. Modification of HC characteristics

Controlling HC characteristics by limiting feedstock type may involve significant difficulties because not all biomass would be appropriate or its cost may limit feedstock usage. Therefore, identifying abundant, low-cost, and reliable biomass is necessary for efficient HC production. In addition, suitable in-situ or post-production modifications should be considered when the resulting product lacks requisite performance characteristics.

The modification of HC properties by changing carbonization temperature and residence time has been reported to have generated materials lacking adsorption capacities to compete with other CBMs. Therefore, further modification processes (e.g., alkali or acid activation) to produce EHCs have been explored to enhance the adsorption of

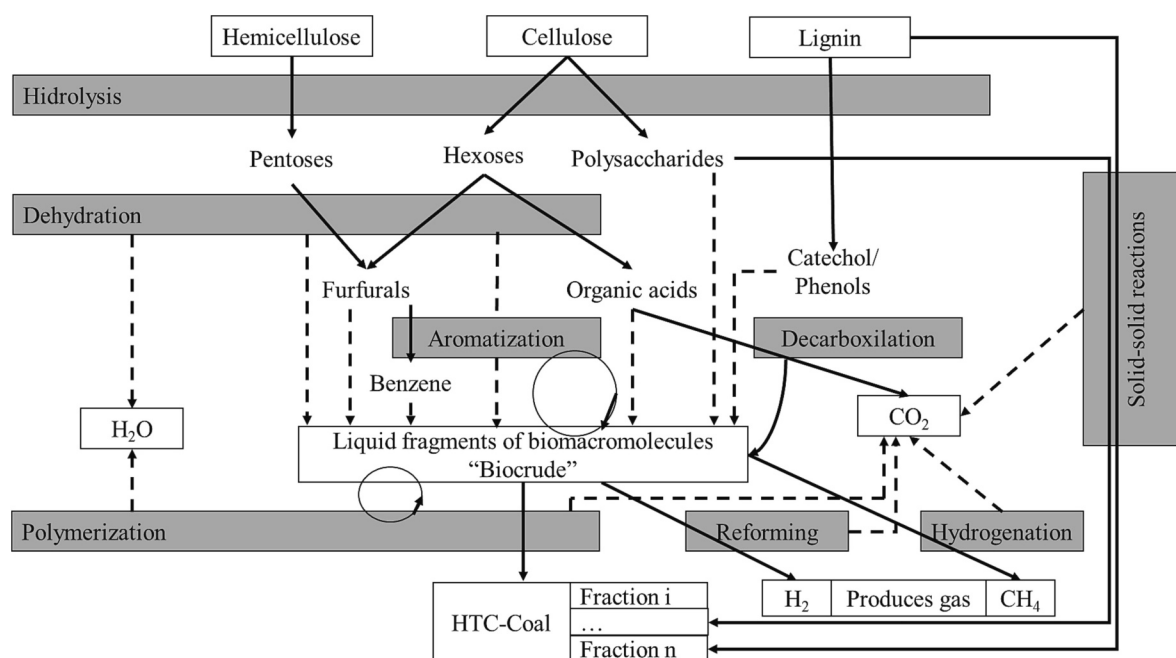


Fig. 1. Schematic of HC formation mechanisms. (Adapted from Kruse et al., 2013) [53].

pollutants in water [19,20,58–60]. For example, alkali activation with KOH has been found to enhance the Pb^{2+} adsorption capability of EHC over five times compared to unmodified HC [35].

EHC is prepared using two main pathways, namely, in-situ treatment and post-treatment. For in-situ HC modification, acid or alkaline solutions are added to the biomass before HTC to promote specific reaction pathways [61]. Post-production modifications involve the addition of chemical agent(s) to change the surface characteristics after HTC. A deeper analysis of how HC production process modification impacts adsorption characteristics is discussed in the following sections.

3.1. Acid/alkaline modification

In-situ modifications. Adding acid or alkaline solutions before HTC accelerates polysaccharide degradation (glucose and furfural production), enhancing HC adsorptive properties [36,59,62]. When acidic conditions are used, protic acids catalyze hydrolysis through nucleophilic substitution accelerating cellulose transformation to glucose [63]. After hydrolysis, dehydration reduces organic molecules (Fig. 1), generating EHC through different pathways. Identifying specific acidic conditions (e.g., acid type and concentration) to limit uncontrolled organic reactions during HC synthesis merits in-depth investigation because it could enable the production of HC with tailored chemical and physical characteristics appropriate for specific applications [64,65]. Very few studies, however, have reported the use of acidic or alkaline solutions as solvents for HTC (Table 1). A more in-depth understanding of the benefits of in-situ acidic or alkaline modifications before HTC is a pending research task that may help to reduce EHC production time and/or improve material homogeneity and performance reliability.

Alkaline conditions lead to saponification during hydrolysis, transforming esters into alcoholic and/or carboxylic groups and reducing EHC functional groups [66]. Alkali counter ions (e.g., Na^+ , K^+) have been reported to produce carboxylate groups on the EHC surface and serve as cation exchange sites [67,68]. However, there is a paucity of information available on alkaline in-situ modification (Table 1), which is another knowledge gap worthy of attention because it would allow the adoption of alternative EHC production pathways to achieve enhanced properties for advanced applications in water treatment.

Post-production modifications. Table 2 shows the different post-production methods reported using alkali, acidic, or oxidant solutions. Alkali post-production activation is the most frequently used method, particularly potassium hydroxide because it is well-known for creating oxygen-containing surface functional groups on EHC and substituting hydrogen in carboxylic groups with potassium [79]. In Table 3, significant surface area and porosity increases are reported for post-production treatment with enhanced HC properties depending on the

synthesis method adopted. Acidic activation consistently produces a higher surface area (ca. two-fold) compared to alkaline activation or unmodified material (Table 3). However, only a limited number of studies were found which have reported using acidic HC activation [34]. There is a significant need to understand the benefits and limitations of alkali and acidic HC activation, which is considered a pending research task that merits further exploration because it can provide essential knowledge for improved EHC synthesis methods and pathways for customized materials for water treatment.

3.2. Modification of functional groups

In-situ modifications. The addition of amino-functional groups has been reported to enhance HC's chemical and physical characteristics [19,59,99]. However, as shown in Table 1, only a few studies have investigated amine HC modification. Ammonium sulfate has been used before HTC, impacting long-chain, liquid by-products (e.g., furfural, 5-methyl furfural) synthesis pathways and the resulting performance was compared with experiments without ammonium sulfate addition [40]. Acetic acid was the only HTC by-product identified when ammonium sulfate was used for HC modification, suggesting changes in the production pathway. No information is available about by-product generation using other production conditions. This is considered a significant knowledge gap that merits further research to better understand the effect of nitrogen compounds on the EHC production pathway and the enhancement of HC adsorption abilities.

Post-production modifications. A two-step post-thermal modification process for EHC has been suggested using acidic or alkaline activation to increase hydroxyl functional groups, followed by amino functionalization to increase nitrogen content [100]. This lack of information is considered an interesting research area worthy of attention to better understand the influence of different chemical modifications for producing EHC with specific functional groups and allowing the addition of amine groups leading to the reduction of synthesis steps.

3.3. Metal functionalized particles

In situ modifications. Few studies are available on variations of chemical and/or physical characteristics after metals addition before HTC (Table 1). Iron-induced polymerization and re-arrangement have been found to activate functional groups on the HC surface [58]. Calcium was found to generate side-chain lignin, ester bond cleavage, and carboxyl group deprotonation when added as HTC alkaline treatment [74]. Little is known about the effects of other metallic elements (e.g., other transition metals, metalloids, rare earths) on HC production. The limited information available suggests that performance improvements

Table 1
In-situ modifications for EHC production.

Modification type	Reagent	Feedstock	Thermal treatment	Reference
Acid treatment	N-cyclohexyl sulfamic acid	Sawdust	190 °C; 12 h; O ₂	[36]
Acid treatment	HCl	Small world rabbit food	250 °C; 20 h; O ₂	[62]
Alkaline treatment	NaOH	Small world rabbit food	250 °C; 20 h; O ₂	[62]
Functional group modification	Ammonium sulfate	Sucrose	200 °C; 4 h; O ₂	[40]
Functional group modification	Triethylenetetramine	Glucose	190 °C; 48 h; O ₂	[69]
Metal immobilization	Fe	Pinewood sawdust	200 °C; 1 h; O ₂	[70]
Metal immobilization	Fe	Pinewood powders	180 °C; 20 h; 10 °C min ⁻¹ ; O ₂	[71]
Metal immobilization	Fe	Sewage sludge	180 °C; 3 h; O ₂	[56]
Metal immobilization	Fe	Rice straw	200 °C; 3 h; O ₂	[58]
Metal immobilization	La	Rice straw	200 °C; 4–14 h; O ₂	[72]
Metal immobilization	Ca	Wood powder	200 °C; 12 h; O ₂	[73]
Metal immobilization	Ca	Pinewood sawdust	220 °C; 4 h; O ₂	[74]
Metal immobilization	Si/Mg	Pine sawdust	180 °C; 12 h; O ₂	[75]
Functional-coated	Ti ₃ AlCl ₂	Glucose	180 °C; 48 h	[76]
		Cellulose		
		Pinewood sawdust		
Functional-coated	Montmorillonite	Microcrystalline cellulose	200 °C; 2–24 h; autogenic pressure; O ₂	[77]
Functional-coated	Zero valent iron	Alkali lignin	200 °C; 18 h	[78]

Table 2
Acidic/alkaline treatment and chemical oxidation for HC modifications.

Chemical treatment	Feedstock	Chemical	Chemical activation	Secondary heat treatment	Reference
Alkaline	Rattan	NaOH	HC/NaOH mass ratio 3:4	600 °C; 1 h; 10 °C min ⁻¹ ; N ₂	[80]
Alkaline	Sewage sludge	KOH	HC/KOH mass ratio 0.5	650 °C; 2.5 h; N ₂ atmosphere	[55]
Alkaline	Sawdust, wheat straw, cornstalk	KOH	HC: 4 gL ⁻¹ ; [KOH]: 2 N	None	[81]
Alkaline	Grape pomace	KOH	HC:10 gL ⁻¹ ; [KOH]:2 M	None	[35]
Alkaline	Commercial sucrose	KOH	KOH/HC mass ratio 1:1–4:1	N ₂ ; 300–800 °C; 2 h; 10 °C min ⁻¹	[79]
Alkaline	Corn cobs	KOH	1:10 HC/KOH; [KOH]:3 M	230, 260 °C; 0.5 h; O ₂	[82]
Alkaline	Rice Husk	KOH	1:3–1:6 KOH/HC	800 °C; 1 h; N ₂	[83]
Alkaline	α-D-glucose	NaOH			
Alkaline	Sucrose	KHCO ₃	4,6,8 KHCO ₃ /HC ratio	N ₂ ; 850 °C; 1-5 h; 5 °C min ⁻¹	[84]
Alkaline	Hickory wood	KOH	1:0.25–1:3 HC/KOH	800 °C; 2 h; 5 °C min ⁻¹ ; N ₂	[85]
Alkaline	Peanut hull	KOH	1:1 KOH/HC; 50 % KOH	600 °C; 1 h; N ₂	[34]
Alkaline	Garlic peel	KOH	1:2 HC/KOH ratio	600–800 °C; 1 h; 2 °C min ⁻¹ ; N ₂	[86]
Acidic	Orange peels	HNO ₃	33.3 gL ⁻¹ HC; 30, 50,70 % HNO ₃	None	[87]
Acidic	D-glucose				
Acidic	Rice Husk	H ₃ PO ₄	1:4,1:6 H ₃ PO ₄ /HC ratio; 85 % H ₃ PO ₄	800 °C; 1 h; N ₂	[83]
Acidic	Hickory wood	H ₃ PO ₄	1:1 H ₃ PO ₄ /HC ratio; 85 % H ₃ PO ₄	600 °C; 1 h; N ₂	[34]
	Peanut hull				
Oxidant	Sawdust	H ₂ O ₂	10 g HC in 300 mL 20%H ₂ O ₂	None	[88]
Oxidant	Peanut hull	H ₂ O ₂	10 g HC in 300 mL 20%H ₂ O ₂	None	[89]

Table 3
Physical characteristics of engineered HC from post-treatment modifications.

Modification	Feedstock	Surface area, m ² g ⁻¹		Porosity, cm ³ g ⁻¹		Reference
		Unmodified	Modified	Unmodified	Modified	
Alkaline/KOH	Garlic peel	306	1262	0.17	0.70	[86]
Alkaline/KOH	Sucrose	33	2604	0.027	1.69	[85]
Alkaline/KOH	α-D-glucose	525	3400	0.22	2.40	[84]
Alkaline/KOH	Sawdust	4.4	0.69	0.013	0.002	[81]
	Wheat straw	9.1	0.42	0.041	0.003	
	Cornstalk	8.6	1.84	0.034	0.006	
Alkaline/KOH	Glucose	75	1197	0.1	0.74	[90]
Alkaline/KOH	Corn cobs	2.8	5.24	0.005	0.011	[82]
Alkaline/KOH	Commercial sucrose	33	2604	0.027	1.44	[79]
Alkaline /KHCO ₃	α-D-glucose	525	3050	0.22	2.10	[84]
Alkaline/K ₂ CO ₃	Salix psammophila	6.9	1230	0.041	0.810	[91]
Alkaline/K ₂ CO ₃	Rice straw derived	6.22	1334	0.06	1.07	[92]
Alkaline/KOH	Hickory wood	8	222	0.121	0.05	[34]
	Peanut hull	7	571	0.01	0.075	
Acid/H ₃ PO ₄	Hickory wood	8	1436	0.121	0.028	[34]
	Peanut hull	7	1091	0.01	0.079	
Acid/HNO ₃	Orange peels	34.1	20.25	0.047	0.042	[87]
	D-glucose	7.3	4.49	0.012	0.012	
Functional group/Protonate amine	Bamboo	26.2	11.76	0.089	0.026	[93]
Functional group/Melamine	Glucose	75	148	0.1	0.15	[90]
Functional group/Triethylenetetramine	Glucose	335	313	0.217	0.144	[69]
Metal immobilization/Fe	Salix psammophila	7.16	349	0.006	0.24	[94]
Metal immobilization/Fe-Ni	Salix psammophila	7.16	515–1351	0.004	0.315–0.549	[95]
Metal immobilization/Fe	Salix psammophila	6.86	673	0.041	0.646	[91]
Metal immobilization/Fe	Coffee waste	17.2	34.7	0.59	0.13	[30]
Metal immobilization/Fe	Rice straw derived	6.22	674	0.06	0.72	[92]
Metal immobilization	Rice Husk	44.47	167.17	0.019	0.065	[96]
Functionalized particles	Sawdust	1.52	13.66	0.004	0.043	[97]
Functionalized particles	Sawdust	1.52	2.97	0.004	0.027	[97]
Functionalized particles	Sawdust	1.52	3.73	0.004	1.348	[97]
Biological modification	Sawdust	3.24	10.33	–	–	[98]

could be achieved using single or hybrid metallic-modified EHCs for adsorbing organic pollutants and heavy metals [101]. Accordingly, understanding in-situ HC modification with metals is a pending research task that merits further investigation to identify alternative production pathways and to create EHC for fit-for-purpose applications.

Post-production modifications. Iron-impregnated EHC has been investigated to understand the effect of iron concentration (e.g., 33 vs. 77 % v/v Fe) on adsorption performance [48]. Post-production modifications were found to generate relatively higher surface area (e.g., 337 vs. 794 m² g⁻¹) and pore volume (i.e., 0.1593 vs. 0.2547 cm³ g⁻¹) compared to in-situ modification. In addition, studies have reported iron association with oxygen-containing functional groups during HTC

leading to improved EHC dispersion. After post-production treatment, Fe ions were found attached to hydrophilic groups by electrostatic attraction within the outer hydration shell. However, no studies are available comparing engineered and non-engineered materials which inhibits the evaluation of different impregnation pathways or understanding chemical and physical characteristics in the resulting EHC. As shown in Table 4, only iron has been investigated and information concerning other metals and metallic ions remains unavailable. This is another significant knowledge gap that merits attention as metallic elements are reported to improve the performance of other CBMs for different applications [102–104].

Using HC to prevent agglomeration and functionalized particle

Table 4
Immobilization of metal composites.

Feedstock	Metal	Magnetic or non-magnetic	Second thermal treatment	Reference
Rice Husk	Ni	Non-magnetic	800 °C; 1 h; O ₂	[104]
Pinewood sawdust	Fe	Non-magnetic	600 °C; 1 h; N ₂ (200 mL min ⁻¹)	[70]
Rice husk	Fe/Mn	Non-magnetic	–	[96]
Rice straw derived	Fe	Magnetic	1.5 h; N ₂ (1 L min ⁻¹)	[92]
Sugarcane bagasse	Fe	Magnetic	–	[111]
Salix psammophila	Fe	Magnetic	700 °C; 2 h; N ₂ (1 L min ⁻¹)	[94]
Salix psammophila	Fe/Ni	Magnetic	500–800 °C; 1.5 h; N ₂ (1 L min ⁻¹)	[95]
Salix psammophila	Fe	Magnetic	70 °C; 3 h; N ₂	[91]
Orange peel	Fe	Magnetic	–	[112]
Coffee waste	Fe	Magnetic	–	[30]

recovery has been reported in past studies [103,105,106]. For example, attaching zero-valent metals (e.g., Fe/Ni) to HC is reported to help prevent oxidation [107,108] and particle agglomeration [109]. However, very few studies are available where HC has been used to support zero-valent metals (Fe/Ni) [109], clays [97], or semiconductors (Ag₃PO₄) [110]. This knowledge, if available, would help to understand the interactions between HC and functionalized particles to reduce the material's limitations (e.g., agglomeration) or generate other properties that may lead to enhanced adsorption ability.

3.4. Other engineered modifications

HC production involves long processing times and uneven heating patterns [113]. Alternative heat treatment (e.g., microwave radiation) has received increasing attention because it is faster and can provide uniform heat transfer [114,115]. Microwave radiation generates selective HC autogenic reactions (i.e., higher acetyl rupturing), which enables the fine-tuning of EHC characteristics [115] at lower production cost [115,116]. No detailed cost analysis has been reported, and the technology readiness level (TRL) remains low preventing fair comparison with other technologies capable of full-scale HC production. This is considered a significant knowledge gap requiring further attention. Microwave-assisted HC production has also been reported pointing towards an interesting future research avenue for EHC production.

Using microorganisms to digest organic matter on HC surface is reported to increase surface area [98] through alkane conversion via anaerobic digestion. The process has been reported to change HC surface charge and hydrophobicity, suggesting that chemical activation modifications could also be achieved using biological treatment [57]. This approach provides the potential to avoid chemical usage, significantly reducing the carbon footprint of the process. Consequently, HC production using biological modifications is a highly interesting research

avenue requiring further exploration, as minimal research has been undertaken to date.

4. EHC adsorption applications

4.1. Heavy metal removal

Heavy metal adsorption using EHC for water treatment (Table 5) is reported as highly cost-effective. For example, iron-modified EHC has been shown to have high adsorption capacity for Pb and Cd ($Q_{max} = 417$ and 323 mg g^{-1} , respectively) [109,111]. However, these studies have used differing experimental conditions preventing fair comparison. The persistent lack of systematic studies with comparable conditions is another significant knowledge gap which merits attention because reporting on HTC conditions and feedstock used in a study is essential to identify specific influences exerted by key variables on EHC characteristics and to assess pollutant adsorption ability and selectivity.

4.2. Adsorption of organic compounds

EHC has been reported to be primarily for dye adsorption (Table 6), where chemical modifications (acid or alkali), functional modifications, and metal immobilization were found to produce encouraging results. Nevertheless, the need for systematic studies with comparable variables (e.g., hydrochar type, dye structure) remains to be investigated to assess the influence of HC modifications and associated structural changes. The need for an in-depth understanding of the adsorption mechanisms involved [120–122] is considered a significant knowledge gap as this knowledge would help to correlate adsorption pathways with HC modifications. Once adsorption pathways are known, the processes can be influenced by specific modifications (e.g., electrostatic attraction, hydrogen bonding) [87]. Other mechanistic pathways (e.g., ion

Table 5
Efficiency of engineered hydrochar for heavy metal removal.

Modification	Contaminant	Removal, %	Notes	Reference
Acid/N-cyclohexyl sulfamic acid	Cu	100	[Cu] ₀ :0–100 mg L ⁻¹ ; [HC]:0.5 g L ⁻¹ ; pH:2–9	[36]
Alkaline/KOH	Cd	20–100	[Cd] ₀ :5–300 mg L ⁻¹ ; [HC]: 2 g L ⁻¹ ; pH: 2–10 30 °C	[81]
Alkaline/KOH	Pb	56–100	[Pb] ₀ : 100 mg L ⁻¹ ; [HC]: 0.4–4 g L ⁻¹ ; pH: 2–7;25,35,45 °C	[35]
Alkaline/KOH	NH ₄ ⁺	75–88	[NH ₄ ⁺] ₀ :1324 mg L ⁻¹ ; [HC]:10 g L ⁻¹ ; pH:4.5–8.5;25, 35, 45 °C	[82]
Functional groups/Triethylenetetramine	Pb	0–100	[Pb] ₀ : 4 g L ⁻¹ ; [Cu] ₀ : 4 g L ⁻¹ ; [HC]:5–1200 mg L ⁻¹ ;pH: 5; 30 °C	[69]
	Cu	0–100		
Functional group/Maleylated	Cd	35–100	[Cd] ₀ : 40–210 mg L ⁻¹ ; [HC]: 0.8 g L ⁻¹ ;pH:2–10; 20–30 °C	[117]
Functional group/Polyaminocarboxylated	Cu	58–100	[Cu] ₀ :40–220 mg L ⁻¹ ; [HC]: 0.8 g L ⁻¹ ;30,40,50 °C;pH:2–5	[118]
Functional groups/Polyethylene imine	Cr	25–100	[Cr] ₀ : 20 mg L ⁻¹ ; [Ni] ₀ : 50 mg L ⁻¹ ; [HC]: 2.5 g L ⁻¹ ;pH: 5.5	[100]
	Ni	50–100		
Immobilized material/Bentonite	NH ₄ ⁺	12–100	[NH ₄ ⁺] ₀ : 200 mg L ⁻¹ ; [HC]: 1–10 g L ⁻¹ ;pH: 6; 30 °C	[119]
Immobilized material/Ti ₃ AlC ₂	Cd	60–10	[Cd] ₀ : 5–100 mg L ⁻¹ ; [Cu] ₀ :5–100 mg L ⁻¹ ; [HC]:1 g L ⁻¹ ; 25°	[76]
	Cu	41–100		
Immobilized material/Lanthanum	P	77–100	[P] ₀ : 40,100 mg L ⁻¹ ; [HC]: 5–4 g L ⁻¹ ; 25 °C	[72]
Immobilized material/Fe	Pb	35–100	[Pb] ₀ : 25, 400 mg L ⁻¹ ; [Cd] ₀ : 25, 400 mg L ⁻¹ ; [HC]: 0.4–2 g L ⁻¹ ;	[111]
	Cd	32–100	pH _{pp} : 1.8–7.1; pH _{Ca} : 2.2–8.5; 25,30,40 °C	
Immobilized material/ Zero valent Ni-Fe	Pb	100	[Pb] ₀ : 50–500 mg L ⁻¹ ; [HC]:2 g L ⁻¹ ; pH:3–6	[109]
Immobilized material/Calcite	Cu	37–100	[Cu] ₀ :30–300 mg L ⁻¹ ; [HC]: 0.8 g L ⁻¹ ; pH: 3–6.5	[73]

Table 6
Efficacy of engineered hydrochar for the removal of organic contaminants.

Modification	Contaminant	Removal, %	Notes	Reference
Acid/HNO ₃	Methylene blue	0–100	[MB] ₀ :0.1–1.0 g L ⁻¹ ;[HC]: 2 g L ⁻¹ ; pH: 2–11; 10, 30,50 °C	[87]
Acid/N-cyclohexyl sulfamic acid	Benzotriazole	85–100	[BTA] ₀ :0–0.1 g L ⁻¹ ; [HC]: 0.5 g L ⁻¹ ; pH: 2–9	[36]
Alkaline/NaOH	Methylene blue	82–100	[MB] ₀ :25–350 mg L ⁻¹ ; [HC]: 0.8 g L ⁻¹ ; pH: 3–11;30 °C	[80]
Functional groups/Triethylenetetramine	Acid Red 1	0–100	[AR1] ₀ :4g L ⁻¹ ;[MG5] ₀ :4g L ⁻¹ ; [HC]:5–1200 mg L ⁻¹ ; pH: 5;30 °C	[69]
	Methylene green 5	0–100		
Functional groups/Protonated amine	Methyl orange	61–100	[MO] ₀ : 0.3–1.2 g L ⁻¹ ; [HC]:0.8 g L ⁻¹ ; pH:4–12	[93]
Functional group/Maleylated	Methylene blue	70–100	[MB] ₀ :0.5–1.3 g L ⁻¹ ;[HC]:0.8 g L ⁻¹ ;pH:2–10;20–30 °C	[117]
Functional group/Quaternary ammonium	Methyl orange	34–100	[MO] ₀ : 0.2–1 g L ⁻¹ ;[HC]: 0.4,1 g L ⁻¹ ; pH:6.2–6.7; 30, 40, 50 °C	[123]
Functional group/Polyaminocarboxylated	Methylene blue	83–100	[MB] ₀ :0.4–1.2 mg L ⁻¹ ;[HC]: 0.8 g L ⁻¹ ; 30, 40, 50 °C; pH:2–10	[118]
Immobilized material/Fe	Malachite green	50–100	[MG] ₀ :125,187,250 mg L ⁻¹ ; [HC]:0.5 g L ⁻¹ ;25,35,45 °C;pH: 2–12	[91]
Immobilized material/Fe-Mn	17 β-estradiol	31–100	[E2] ₀ :0.2–8 mg L ⁻¹ ;[HC]: 0.05 g L ⁻¹ ;pH:3–12; 28 °C	[96]
Immobilized material/Fe	Triclosan	38–100	[TCS] ₀ :10–40 mg L ⁻¹ ; [HC]: 50 mg L ⁻¹ ; pH:3–10	[92]
Immobilized material/Fe	Tetracycline	31–100	[TC] ₀ :5–80 mg L ⁻¹ ; [HC]: 1 g L ⁻¹ ;25–43 °C	[94]
Immobilized material/Fe	Triclosan	100	[TCS] ₀ :10–50 mg L ⁻¹ ;[HC]: 500 mg L ⁻¹ ;pH:2–4; 30 °C	[95]

exchange) have been proposed for methyl orange adsorption using HC functionalized with quaternary ammonium groups [123]. Despite the high efficiency shown by HC for the adsorption of organic and inorganic compounds (Tables 5 and 6), little is known about the efficacy of EHC for the adsorption of emerging contaminants (Table 6). This is considered another significant knowledge gap that merits attention based on the successful use of other engineered CBMs for the adsorption of emerging contaminants [103,124].

5. Life cycle analysis (LCA)

LCA evaluates the environmental, social, or economic impacts associated with all stages of the life cycle of a commercial product, process or service. The process collects information that is analyzed depending on the major stages of the product/process/service life. Environmental LCA (LCA-E) follows a sequence of steps that address one or more life stages at a time, starting by setting a goal and scope and performing a life cycle inventory followed by a life cycle impact assessment (Fig. 2) [125,126]. Once the inventory analysis is completed, the impact assessment focuses on classifying the environmental impacts of all the processes involved and modeling and translating these into potential impacts such as human health, ecosystem quality, climate change impacts, and resource usage (e.g., use of non-renewable energy) [127]. Fig. 3 illustrates the LCA process and interactions between different steps along with different impact categories and associated impacts [128].

5.1. LCA-E for EHC

To date, very few studies have been devoted to LCA-E for HC

production and most of these have focused on broad goals and scope (initial LCA steps, Fig. 3), assessing environmental impacts, identifying critical production parameters or comparing performance with similar materials [128–130] (Table 7). As shown in Table 7, only one study was found on LCA-E for EHC where acetic acid was used as a catalyst for EHC production [131]. Understanding the environmental impacts generated by EHC and unmodified HC production for different boundary conditions (e.g., cradle-to-grave, production only) and applying LCA-E is an important research avenue worthy of further investigation.

Energy consumption contributes to HC environmental impacts accounting for at least 50 % of the overall greenhouse emissions (GHE) [132–134]. As a result, energy conservation is usually a major task when investigating HTC and materials with short detention times are preferred (Table 7). From Table 1, however, in situ produced materials are reported with detention times 3 times longer than other materials and, therefore, improving synthesis methods with reduced detention time has become an urgent pending research task. Further, energy consumption analysis of modified materials prepared using post-treatment (see Tables 2 and 4) suggests that a high amount of energy is required for the two processes used to produce CBMs. This has significant negative impacts related to greenhouse gas emissions and seriously threatens the environmental viability. Hence, LCA-E studies comparing energy consumption for the same material using in situ and post-treatment are needed to fill this knowledge gap.

From LCA-E standpoint, feedstock influences the impacts associated with the collection, processing and disposal (i.e., LCA-E inventory) by contributing to emissions depending on where feedstock is collected, the resources used to move the feedstock from the collection point to the processing point [135], feedstock characteristics, and desired EHC properties [40,127,134].

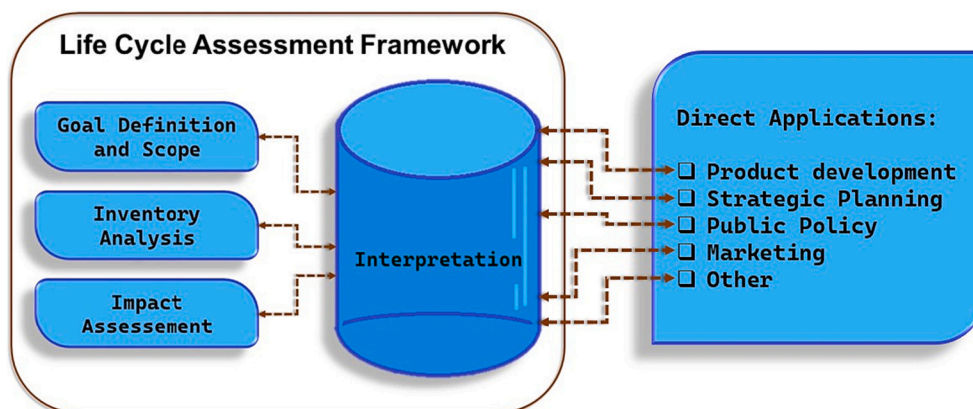


Fig. 2. Steps of an LCA.

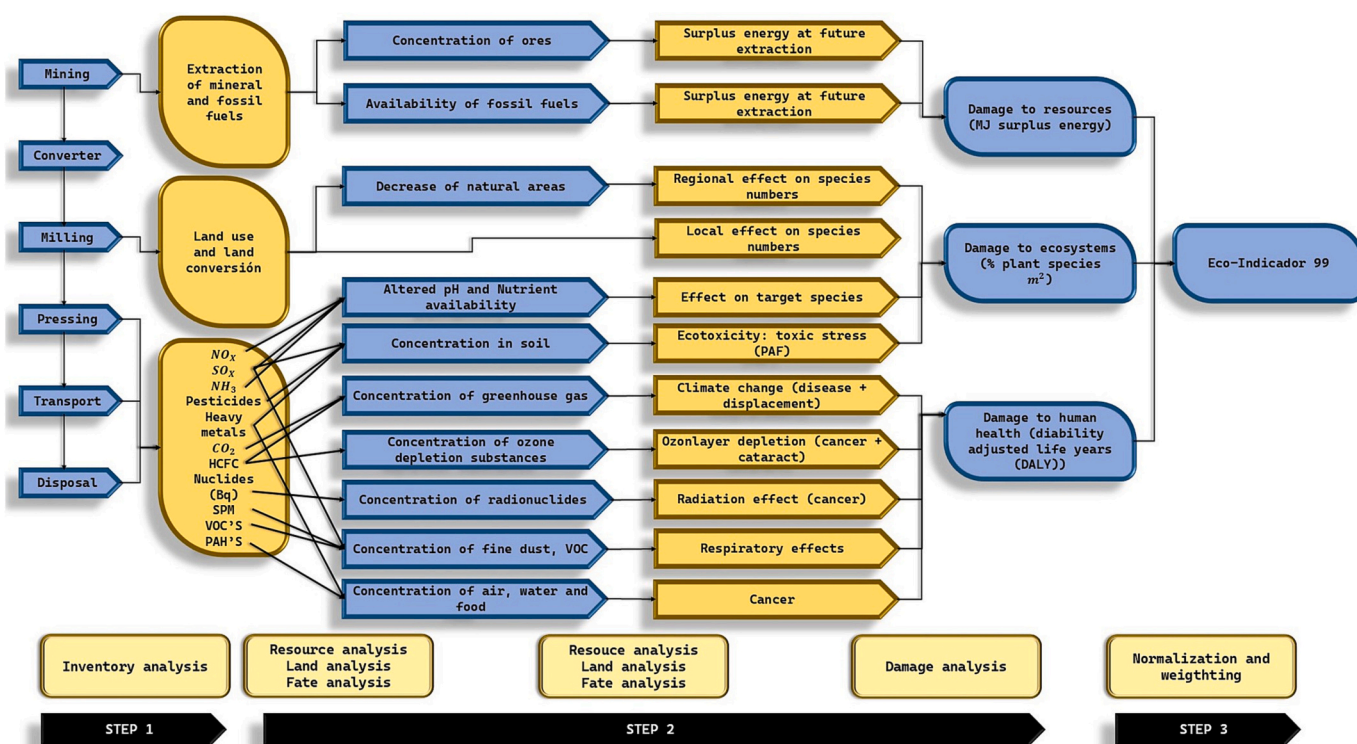


Fig. 3. LCA steps and interactions and different impact categories and associated impacts.

Table 7
LCA studies on EHC.

Feedstock	HTC treatment	EHC application	Reference
Olive mill waste	200, 225. and 250 °C, 2 h	Energy production	[125]
Poultry litter	180–250 °C, 1:3 s/w ratio, 1 h	Energy production	[141]
Food waste	Enzymatic pretreatment, 150, 250, 350 °C, 1:4 s/w ratio, 20 min	Energy production	[133]
Sewage sludge	220 °C, 4 h	Agriculture, Energy	[132]
Sewage sludge	170, 210 °C, 2,10 h	Agriculture, Energy	[126]
Olive Pomace	170, 210 °C, 2, 10 h	Energy	[134]
Sugarcane bagasse	240 °C, 30 min	Energy	[130]
Sewage sludge	208° C, 1 h	Energy	[139]
Peat moss	240 °C, 15 min	Energy, Agriculture	[140]
Miscanthus		Agriculture	
<i>Chlorella vulgaris</i>	180–220 °C, 45 min, 10 wt% acetic acid	Energy	[131]
Green waste	NR	Energy	[127]
Food and packing	225, 250, 275 °C, 4, 16, 96 h	Energy	[129]

LCA-E boundaries are defined depending on the process selected for analysis (Fig. 4) [136]. When the LCA-E boundary focuses on EHC production, feedstock particle size has been found to dictate the required pretreatment [137,138] involving higher energy consumption for small-size feedstock. Some biological pretreatments (e.g., enzymatic, anaerobic digestion) can generate small-size particles without increasing the environmental impacts [125,133,139]. However, very little is known about these approaches and further research is required to better understand the trade-offs involved which is also identified as a knowledge gap requiring further investigation [98].

HTC generates gas, liquid and solid by-products from which only the

solid (i.e., HC) product has been studied with some detail. Only a limited number of studies are available where the other two phases have been investigated [40], which makes the information available on EHC production inadequate for a comprehensive LCA-E. The three main by-products must be included to realistically identify the overall environmental impacts [132,140]. For example, in some cases, the generated biogas mix could be recycled for heating thereby reducing the environmental impacts [131], while in some others, the feedstock (e.g., poultry litter), can produce toxic gases resulting in negative environmental impacts (e.g., H₂S, NO_x, SO₂) and may not be suitable for HC production [141]. Liquid phase by-products, depending on their chemical composition, could be distilled to recover valuable components with the potential for reuse [127,129,141].

Few studies have analyzed LCA-E for EHC with a focus on agricultural applications with most of them reporting significantly low environmental impacts [126,140]. No studies on LCA-E for EHC applications in water treatment are available, generating a significant knowledge gap worthy of attention as the potential for reuse of exhausted materials has been suggested for enhancing agricultural production.

6. Conclusions

EHC production and application for water treatment is a continuously expanding research field. Significant knowledge gaps remain constraining wider EHC applications. The following are the main findings of this study:

- EHC is used for organic and inorganic contaminants adsorption. It is considered an environmentally friendly biosorbent with relatively low environmental impacts compared to other CBMs. Nevertheless, environmental impact analysis is needed to ensure a fair comparison with other similar materials and for use in different treatment applications.
- In-situ HTC produces EHC through selective production pathways. However, the way different key factors influence production

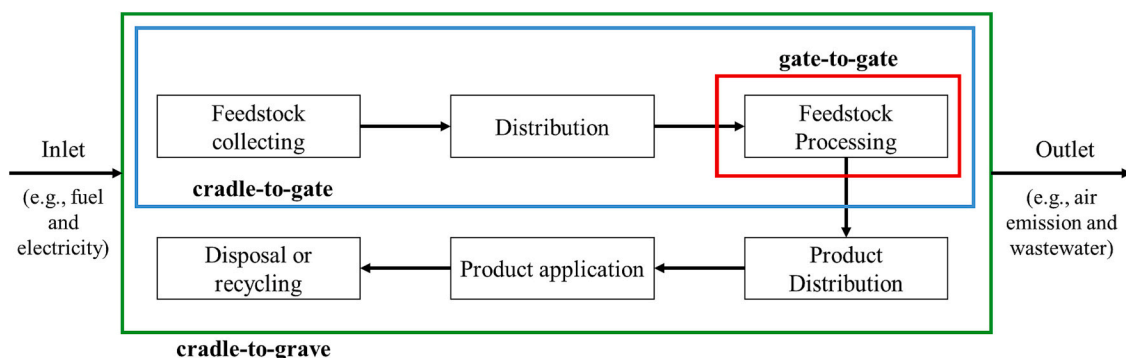


Fig. 4. LCA-E boundary delimitation.

pathways and constraining synthesis process optimization remains poorly understood.

- Post-treatment modifications are the most frequently reported for EHC production. However, better in-depth knowledge of the synthesis process and standardized methods are needed.
- LCA-E has been used to identify the environmental impacts of CBM production. Only a limited number of LCA-E studies on HC and EHC production are available, resulting in a dearth of knowledge and significantly constraining the assessment of the factual contribution of EHC to the circular economy.
- EHC materials' hazards analysis is a factor to be considered in LCA-E. However, little is known on the topic, highlighting a significant knowledge gap because LCA-E cannot be accurately undertaken without toxicity information.
- Narrowing down LCA-E to the production process for EHC could create an acceptable approach. Nevertheless, process boundaries should encompass feedstock collection and process application to better understand the environmental benefits of a specific material.

Declaration of competing interest

The authors declare the following financial interests/personal relationships which may be considered as potential competing interests: Oscar Manuel Rodriguez Narvaez reports financial support and equipment, drugs, or supplies were provided by Guanajuato State Government.

Data availability

No data was used for the research described in the article.

Acknowledgment

O.M. Rodriguez-Narvaez would also like to thank CONACyT for the fellowship to undertake this research study. Also, IDEAGto for the grant for this project (grants: CONVO/045/2021 and CONVO/091/2021). V. A.S.-T. thanks to IxM-CONACYT Program (Project CIR/0064/2022).

References

- [1] M. Mainardis, D. Cecconet, A. Moretti, A. Callegari, D. Goi, S. Freguia, A. G. Capodaglio, Wastewater fertigation in agriculture: issues and opportunities for improved water management and circular economy, *Environ. Pollut.* 296 (2022), 118755, <https://doi.org/10.1016/j.envpol.2021.118755>.
- [2] M.M. Khan, S.A. Siddiqi, A.A. Farooque, Q. Iqbal, S.A. Shahid, M.T. Akram, S. Rahman, W. Al-Busaidi, I. Khan, Towards Sustainable Application of Wastewater in Agriculture: A Review on Reusability and Risk Assessment, *Agron.* 2022, Vol. 12, Page 1397 12, 2022, p. 1397, <https://doi.org/10.3390/AGRONOMY12061397>.
- [3] U. Kumari, S. Biswas, B.C. Meikap, Defluoridation characteristics of a novel adsorbent developed from ferroalloy electric arc furnace slag: batch, column study and treatment of industrial wastewater, *Environ. Technol. Innov.* 18 (2020), 100782, <https://doi.org/10.1016/j.eti.2020.100782>.
- [4] U. Kumari, H. Siddiqi, M. Bal, B.C. Meikap, Calcium and zirconium modified acid activated alumina for adsorptive removal of fluoride: performance evaluation, kinetics, isotherm, characterization and industrial wastewater treatment, *Adv. Powder Technol.* 31 (2020) 2045–2060, <https://doi.org/10.1016/j.apt.2020.02.035>.
- [5] M.R. Awual, M.M. Hasan, A.M. Asiri, M.M. Rahman, Cleaning the arsenic(V) contaminated water for safe-guarding the public health using novel composite material, *Compos. Part B Eng.* 171 (2019) 294–301, <https://doi.org/10.1016/j.compositesb.2019.05.078>.
- [6] M.S. Salman, M.N. Hasan, M.M. Hasan, K.T. Kubra, M.C. Sheikh, A.I. Rehan, R. M. Waliullah, A.I. Rasee, M.E. Awual, M.S. Hossain, A.K.D. Alsukaibi, H. M. Alshammari, M.R. Awual, Improving copper(II) ion detection and adsorption from wastewater by the ligand-functionalized composite adsorbent, *J. Mol. Struct.* 1282 (2023), 135259, <https://doi.org/10.1016/j.molstruc.2023.135259>.
- [7] A.I. Rehan, A.I. Rasee, M.E. Awual, R.M. Waliullah, M.S. Hossain, K.T. Kubra, M. S. Salman, M.M. Hasan, M.N. Hasan, M.C. Sheikh, H.M. Marwani, M.A. Khaleque, A. Islam, M.R. Awual, Improving toxic dye removal and remediation using novel nanocomposite fibrous adsorbent, *Colloids Surfaces A Physicochem. Eng. Asp.* 673 (2023), <https://doi.org/10.1016/j.colsurfa.2023.131859>.
- [8] M.R. Awual, M.M. Hasan, J. Iqbal, A. Islam, M.A. Islam, A.M. Asiri, M. M. Rahman, Naked-eye lead(II) capturing from contaminated water using innovative large-pore facial composite materials, *Microchem. J.* 154 (2020), 104585, <https://doi.org/10.1016/j.microc.2019.104585>.
- [9] M. Kumar, S. Ambika, A. Hassani, P.V. Nidheesh, Waste to catalyst: role of agricultural waste in water and wastewater treatment, *Sci. Total Environ.* 858 (2023), 159762, <https://doi.org/10.1016/j.scitotenv.2022.159762>.
- [10] U. Kumari, A. Mishra, H. Siddiqi, B.C. Meikap, Effective defluoridation of industrial wastewater by using acid modified alumina in fixed-bed adsorption column: experimental and breakthrough curves analysis, *J. Clean. Prod.* 279 (2021), 123645, <https://doi.org/10.1016/j.jclepro.2020.123645>.
- [11] S. Biswas, S. Sharma, S. Mukherjee, B.C. Meikap, T.K. Sen, Process modelling and optimization of a novel Semifluoridized bed adsorption column operation for aqueous phase divalent heavy metal ions removal, *J. Water Process Eng.* 37 (2020), 101406, <https://doi.org/10.1016/j.jwpe.2020.101406>.
- [12] U. Kumari, S.K. Behera, B.C. Meikap, A novel acid modified alumina adsorbent with enhanced defluoridation property: kinetics, isotherm study and applicability on industrial wastewater, *J. Hazard. Mater.* 365 (2019) 868–882, <https://doi.org/10.1016/j.jhazmat.2018.11.064>.
- [13] K.K. Chenab, B. Sohrabi, A. Jafari, S. Ramakrishna, Water treatment: functional nanomaterials and applications from adsorption to photodegradation, *Mater. Today Chem.* 16 (2020), 100262, <https://doi.org/10.1016/j.mtchem.2020.100262>.
- [14] R.K. Singh, R. Kumar, D.P. Singh, Graphene oxide: strategies for synthesis, reduction and frontier applications, *RSC Adv.* 6 (2016) 64993–65011, <https://doi.org/10.1039/c6ra07626b>.
- [15] M.R. Awual, M.N. Hasan, M.M. Hasan, M.S. Salman, M.C. Sheikh, K.T. Kubra, M. S. Islam, H.M. Marwani, A. Islam, M.A. Khaleque, R.M. Waliullah, M.S. Hossain, A.I. Rasee, A.I. Rehan, M.E. Awual, Green and robust adsorption and recovery of Europium(III) with a mechanism using hybrid donor conjugate materials, *Sep. Purif. Technol.* 319 (2023), 124088, <https://doi.org/10.1016/j.seppur.2023.124088>.
- [16] M.M. Hasan, M.S. Salman, M.N. Hasan, A.I. Rehan, M.E. Awual, A.I. Rasee, R. M. Waliullah, M.S. Hossain, K.T. Kubra, M.C. Sheikh, M.A. Khaleque, H. M. Marwani, A. Islam, M.R. Awual, Facial conjugate adsorbent for sustainable Pb (II) ion monitoring and removal from contaminated water, *Colloids Surfaces A Physicochem. Eng. Asp.* 673 (2023), 131794, <https://doi.org/10.1016/j.colsurfa.2023.131794>.
- [17] M.R. Awual, M.M. Hasan, J. Iqbal, M.A. Islam, A. Islam, S. Khandaker, A.M. Asiri, M.M. Rahman, Ligand based sustainable composite material for sensitive nickel (II) capturing in aqueous media, *J. Environ. Chem. Eng.* 8 (2020), 103591, <https://doi.org/10.1016/j.jece.2019.103591>.
- [18] M.S. Salman, M.C. Sheikh, M.M. Hasan, M.N. Hasan, K.T. Kubra, A.I. Rehan, M. E. Awual, A.I. Rasee, R.M. Waliullah, M.S. Hossain, M.A. Khaleque, A.K. D. Alsukaibi, H.M. Alshammari, M.R. Awual, Chitosan-coated cotton fiber

- composite for efficient toxic dye encapsulation from aqueous media, *Appl. Surf. Sci.* 622 (2023), 157008, <https://doi.org/10.1016/J.APSUSC.2023.157008>.
- [19] Z. Zhang, Z. Zhu, B. Shen, L. Liu, Insights into biochar and hydrochar production and applications: a review, *Energy* 171 (2019) 581–598, <https://doi.org/10.1016/j.energy.2019.01.035>.
- [20] A.A. Azzaz, B. Khiari, S. Jellali, C.M. Ghimbeu, M. Jeguirim, Hydrochars production, characterization and application for wastewater treatment: a review, *Renew. Sustain. Energy Rev.* 127 (2020), <https://doi.org/10.1016/j.rser.2020.109882>.
- [21] U. Kumari, S.K. Behera, H. Siddiqui, B.C. Meikap, Facile method to synthesize efficient adsorbent from alumina by nitric acid activation: batch scale defluorination, kinetics, isotherm studies and implementation on industrial wastewater treatment, *J. Hazard. Mater.* 381 (2020), 120917, <https://doi.org/10.1016/J.JHAZMAT.2019.120917>.
- [22] M.M.N. Hasan, K.T. Kubra, M.M.N. Hasan, M.E.M.R. Awwal, M.S. Salman, M. C. Sheikh, A.I. Rehan, A.I. Rasee, R.M. Waliullah, M.S. Islam, S. Khandaker, A. Islam, M.S. Hossain, A.K.D. Alsukaibi, H.M. Alshammari, M.E.M.R. Awwal, Sustainable ligand-modified based composite material for the selective and effective cadmium(II) capturing from wastewater, *J. Mol. Liq.* 371 (2023), 121125, <https://doi.org/10.1016/J.MOLLIQ.2022.121125>.
- [23] P.M. Chee, H. Chia, Adriana Downie, Characteristics of biochar: physical and structural properties, in: *Biochar Environ. Manag.*, Taylor & Francis, 2019, pp. 1–2, <https://doi.org/10.4324/9780203762264-12>.
- [24] X. Chen, W. Da Oh, T.T. Lim, Graphene- and CNTs-based carbocatalysts in persulfate activation: material design and catalytic mechanisms, *Chem. Eng. J.* 354 (2018) 941–976, <https://doi.org/10.1016/j.cej.2018.08.049>.
- [25] E.R. Bandala, A. Liu, B. Wijesiri, A.B. Zeidman, A. Goonetilleke, Emerging materials and technologies for landfill leachate treatment: a critical review, *Environ. Pollut.* 291 (2021), 118133, <https://doi.org/10.1016/J.ENVPOL.2021.118133>.
- [26] O.M. Rodríguez-Narvaez, D.A. Medina-Orendain, L.N. Mendez-Alvarado, Functionalized green carbon-based nanomaterial for environmental application, in: *Sustain. Nanotechnol. Environ. Remediat.*, Elsevier, 2022, pp. 347–382, <https://doi.org/10.1016/B978-0-12-824547-7.00005-9>.
- [27] Q. Zhao, Q. Mao, Y. Zhou, J. Wei, X. Liu, J. Yang, L. Luo, J. Zhang, H. Chen, H. Chen, L. Tang, Metal-free carbon materials-catalyzed sulfate radical-based advanced oxidation processes: a review on heterogeneous catalysts and applications, *Chemosphere* 189 (2017) 224–238, <https://doi.org/10.1016/j.chemosphere.2017.09.042>.
- [28] A. Zaniias, Z. Frontistis, J. Vakros, O.S. Arvaniti, R.S. Ribeiro, A.M.T. Silva, J. L. Faria, H.T. Gomes, D. Mantzavinos, Degradation of methylparaben by sonocatalysis using a Co-Fe magnetic carbon xerogel, *Ultrason. Sonochem.* 64 (2020), 105045, <https://doi.org/10.1016/j.ultrsonch.2020.105045>.
- [29] R. Xiao, Z. Luo, Z. Wei, S. Luo, R. Spinney, W. Yang, D.D. Dionysiou, Activation of peroxymonosulfate/persulfate by nanomaterials for sulfate radical-based advanced oxidation technologies, *Curr. Opin. Chem. Eng.* 19 (2018) 51–58, <https://doi.org/10.1016/j.coche.2017.12.005>.
- [30] A. Khataee, B. Kayan, D. Kalderis, A. Karimi, S. Akay, M. Konsolakis, Ultrasound-assisted removal of acid red 17 using nanosized Fe₃O₄-loaded coffee waste hydrochar, *Ultrason. Sonochem.* 35 (2017) 72–80, <https://doi.org/10.1016/j.ultrsonch.2016.09.004>.
- [31] O.M. Rodríguez-Narvaez, J.M. Peralta-Hernandez, A. Goonetilleke, E.R. Bandala, Treatment Technologies for Emerging Contaminants in water: a review, *Chem. Eng. J.* 323 (2017) 361–380, <https://doi.org/10.1016/j.cej.2017.04.106>.
- [32] D. Kalderis, G. Papametiou, B. Kayan, Assessment of orange peel hydrochar as a soil amendment: impact on clay soil physical properties and potential phytotoxicity, *Waste Biomass Valorization*. 10 (2019) 3471–3484, <https://doi.org/10.1007/s12649-018-0364-0>.
- [33] K. Sheng, S. Zhang, J. Liu, E. Shuang, C. Jin, Z. Xu, Hydrothermal carbonization of cellulose and xylan into hydrochars and application on glucose isomerization, *J. Clean. Prod.* 237 (2019), 117831, <https://doi.org/10.1016/j.jclepro.2019.117831>.
- [34] X. Zhang, B. Gao, J. Fang, W. Zou, L. Dong, C. Cao, J. Zhang, Y. Li, H. Wang, Chemically activated hydrochar as an effective adsorbent for volatile organic compounds (VOCs), *Chemosphere* 218 (2019) 680–686, <https://doi.org/10.1016/j.chemosphere.2018.11.144>.
- [35] J.T. Petrović, M.D. Stojanović, J.V. Milojković, M.S. Petrović, T.D. Šostarić, M. D. Laušević, M.L. Mihajlović, Alkali modified hydrochar of grape pomace as a perspective adsorbent of Pb²⁺ from aqueous solution, *J. Environ. Manage.* 182 (2016) 292–300, <https://doi.org/10.1016/j.jenvman.2016.07.081>.
- [36] J. Deng, X. Li, X. Wei, Y. Liu, J. Liang, N. Tang, B. Song, X. Chen, X. Cheng, Sulfamic acid modified hydrochar derived from sawdust for removal of benzotriazole and Cu(II) from aqueous solution: adsorption behavior and mechanism, *Bioresour. Technol.* 290 (2019), 121765, <https://doi.org/10.1016/j.biortech.2019.121765>.
- [37] M. Mihajlović, J. Petrović, M. Stojanović, J. Milojković, Z. Lopčić, M. Koprivica, Č. Lačnjevac, Hydrochars, perspective adsorbents of heavy metals: a review of the current state of studies, *Zast. Mater.* 57 (2016) 488–495, <https://doi.org/10.5937/zasmat1603488m>.
- [38] S. Nizamuddin, A. Jadhav, S.S. Qureshi, H.A. Baloch, Synthesis and characterization of polylactide / rice husk hydrochar composite, *Sci. Rep.* 9 (2019) 1–11, <https://doi.org/10.1038/s41598-019-41960-1>.
- [39] S. Nizamuddin, S.S. Qureshi, H.A. Baloch, M.T.H. Siddiqui, P. Takkalkar, N. M. Mubarak, D.K. Dumbre, G.J. Griffin, S. Madapusi, A. Tanksale, Microwave hydrothermal carbonization of rice straw: optimization of process parameters and upgrading of chemical, fuel, structural and thermal properties, *Materials* (Basel). 12 (2019), <https://doi.org/10.3390/ma12030403>.
- [40] K.G. Latham, G. Jambu, S.D. Joseph, S.W. Donne, Nitrogen doping of hydrochars produced hydrothermal treatment of sucrose in H₂O, H₂SO₄, and NaOH, *ACS Sustain. Chem. Eng.* 2 (2014) 755–764, <https://doi.org/10.1021/sc40044339>.
- [41] E. Diaz, F.J. Manzano, J. Villamil, J.J. Rodríguez, A.F. Mohedano, Low-cost activated grape seed-derived hydrochar through hydrothermal carbonization and chemical activation for sulfamethoxazole adsorption, *Appl. Sci.* 9 (2019) 5127, <https://doi.org/10.3390/app9235127>.
- [42] C. Huang, B.A. Mohamed, L.Y. Li, Comparative life-cycle assessment of pyrolysis processes for producing bio-oil, biochar, and activated carbon from sewage sludge, *Resour. Conserv. Recycl.* 181 (2022), 106273, <https://doi.org/10.1016/j.resconrec.2022.106273>.
- [43] D. Mohan, A. Sarawat, Y.S. Ok, C.U. Pittman, Organic and inorganic contaminants removal from water with biochar, a renewable, low cost and sustainable adsorbent - a critical review, *Bioresour. Technol.* 160 (2014) 191–202, <https://doi.org/10.1016/j.biortech.2014.01.120>.
- [44] H.S. Kambo, A. Dutta, A comparative review of biochar and hydrochar in terms of production, physico-chemical properties and applications, *Renew. Sustain. Energy Rev.* 45 (2015) 359–378, <https://doi.org/10.1016/J.RSER.2015.01.050>.
- [45] M. Sasaki, Z. Fang, Y. Fukushima, T. Adschiri, K. Arai, Dissolution and hydrolysis of cellulose in subcritical and supercritical water, *Ind. Eng. Chem. Res.* 39 (2000) 2883–2890, <https://doi.org/10.1021/IE990690J>.
- [46] R.O.L. Souza, D.P. Fabiano, C. Feche, F. Rataboul, D. Cardoso, N. Essayem, Glucose-fructose isomerisation promoted by basic hybrid catalysts, *Catal. Today* 195 (2012) 114–119, <https://doi.org/10.1016/J.CATTOD.2012.05.046>.
- [47] M.B. Fusaro, V. Chagnault, D. Postel, Reactivity of d-fructose and d-xylose in acidic media in homogeneous phases, *Carbohydr. Res.* 409 (2015) 9–19, <https://doi.org/10.1016/J.CARRES.2015.03.012>.
- [48] A. Funke, F. Ziegler, Hydrothermal Carbonization of Biomass: A Summary and Discussion of Chemical Mechanisms for Process Engineering, John Wiley & Sons, Ltd, 2010, <https://doi.org/10.1002/bbb.198>.
- [49] S. Kumar, Sub- and supercritical water technology for biofuels, *Adv. Biofuels Bioprod.* 9781461433484 (2013) 147–183, https://doi.org/10.1007/978-1-4614-3348-4_11/FIGURES/14.
- [50] G. Shen, B. Andrioletti, Y. Queneau, Furfural and 5-(hydroxymethyl)furfural: two pivotal intermediates for bio-based chemistry, *Curr. Opin. Green Sustain. Chem.* 26 (2020), 100384, <https://doi.org/10.1016/J.COCS.2020.100384>.
- [51] A. Jain, R. Balasubramanian, M.P. Srinivasan, Hydrothermal conversion of biomass waste to activated carbon with high porosity: a review, *Chem. Eng. J.* 283 (2016) 789–805, <https://doi.org/10.1016/J.CEJ.2015.08.014>.
- [52] S. Masoumi, V.B. Borugadda, S. Nanda, A.K. Dalai, Hydrochar: A Review on Its Production Technologies and Applications, *Catal.* 2021, Vol. 11, Page 939 11, 2021, p. 939, <https://doi.org/10.3390/CATAL11080939>.
- [53] A. Kruse, A. Funke, M.M. Titirici, Hydrothermal conversion of biomass to fuels and energetic materials, *Curr. Opin. Chem. Biol.* 17 (2013) 515–521, <https://doi.org/10.1016/j.cbpa.2013.05.004>.
- [54] M. Mäkelä, V. Benavente, A. Fullana, Hydrothermal carbonization of lignocellulosic biomass: effect of process conditions on hydrochar properties, *Appl. Energy* 155 (2015) 576–584, <https://doi.org/10.1016/j.apenergy.2015.06.022>.
- [55] A.L. Tasca, D. Clematis, P. Marco, S. Vitolo, M. Puccini, Herbicide removal from water: investigating the potential of electrochemistry and hydrochar-based activated carbon, *Chem. Eng. Trans.* 74 (2019) 841–846, <https://doi.org/10.33031/CET1974141>.
- [56] J. Wei, Y. Liu, Y. Zhu, J. Li, Enhanced catalytic degradation of tetracycline antibiotic by persulfate activated with modified sludge bio-hydrochar, *Chemosphere* 247 (2020), 125854, <https://doi.org/10.1016/j.chemosphere.2020.125854>.
- [57] R. Kaushik, G.K. Parshetti, Z. Liu, R. Balasubramanian, Enzyme-assisted hydrothermal treatment of food waste for co-production of hydrochar and bio-oil, *Bioresour. Technol.* 168 (2014) 267–274, <https://doi.org/10.1016/j.biortech.2014.03.022>.
- [58] K. Nadarajah, E.R. Bandala, Z. Zhang, S. Mundree, A. Goonetilleke, Removal of heavy metals from water using engineered hydrochar: kinetics and mechanistic approach, *J. Water Process Eng.* 40 (2021), 101929, <https://doi.org/10.1016/j.jwpe.2021.101929>.
- [59] T. Wang, Y. Zhai, Y. Zhu, C. Li, G. Zeng, A review of the hydrothermal carbonization of biomass waste for hydrochar formation: process conditions, fundamentals, and physicochemical properties, *Renew. Sustain. Energy Rev.* 90 (2018) 223–247, <https://doi.org/10.1016/j.rser.2018.03.071>.
- [60] J. Fang, L. Zhan, Y.S. Ok, B. Gao, Minireview of potential applications of hydrochar derived from hydrothermal carbonization of biomass, *J. Ind. Eng. Chem.* 57 (2018) 15–21, <https://doi.org/10.1016/j.jiec.2017.08.026>.
- [61] S. Zhang, X. Zhu, S. Zhou, H. Shang, J. Luo, D.C.W. Tsang, Hydrothermal Carbonization for Hydrochar Production and its Application, Elsevier Inc., 2019, <https://doi.org/10.1016/b978-0-12-811729-3.00015-7>.
- [62] J.F.R. Flora, X. Lu, L. Li, J.R.V. Flora, N.D. Berge, The effects of alkalinity and acidity of process water and hydrochar washing on the adsorption of atrazine on hydrothermally produced hydrochar, *Chemosphere* 93 (2013) 1989–1996, <https://doi.org/10.1016/j.chemosphere.2013.07.018>.
- [63] Z. Wang, H. Ma, Mechanisms of a Cyclobutane-fused Lactone Hydrolysis in Alkaline and Acidic Conditions, *Mol.* 2021, Vol. 26, Page 3519 26, 2021, p. 3519, <https://doi.org/10.3390/MOLECULES26123519>.

- [64] W. Suprun, M. Lutecki, T. Haber, H. Papp, Acidic catalysts for the dehydration of glycerol: activity and deactivation, *J. Mol. Catal. A Chem.* 309 (2009) 71–78, <https://doi.org/10.1016/j.molcata.2009.04.017>.
- [65] C. Tebes-Stevens, J.M. Patel, W.J. Jones, E.J. Weber, Prediction of hydrolysis products of organic chemicals under environmental pH conditions, *Environ. Sci. Technol.* 51 (2017) 5008–5016, <https://doi.org/10.1021/ACS.EST.6B05412>.
- [66] R. Lukajtis, P. Rybaczky, K. Kucharska, D. Konopacka-Lyskawa, E. Słupek, K. Wygodnik, M. Kamiński, Optimization of Saccharification Conditions of Lignocellulosic Biomass under Alkaline Pre-Treatment and Enzymatic Hydrolysis, *Energies* 2018, Vol. 11, Page 886 11, 2018, p. 886, <https://doi.org/10.3390/EN11040886>.
- [67] O.I. Kolodiazny, A. Kolodiazna, Nucleophilic substitution at phosphorus: stereochemistry and mechanisms, *Tetrahedron Asymmetry* 28 (2017) 1651–1674, <https://doi.org/10.1016/j.tetasy.2017.10.022>.
- [68] T.D. Campbell, C.A. Hart, R. Febrian, M.L. Chenel, P.J. Bracher, The opposite effect of K⁺ and Na⁺ on the hydrolysis of linear and cyclic dipeptides, *Tetrahedron Lett.* 59 (2018) 2264–2267, <https://doi.org/10.1016/j.tetlet.2018.04.073>.
- [69] H.N. Tran, F.C. Huang, C.K. Lee, H.P. Chao, Activated carbon derived from spherical hydrochar functionalized with triethylenetetramine: synthesis, characterizations, and adsorption application, *Green Process. Synth.* 6 (2017) 565–576, <https://doi.org/10.1515/gps-2016-0178>.
- [70] C. Gai, F. Zhang, Q. Lang, T. Liu, N. Peng, Z. Liu, Facile one-pot synthesis of iron nanoparticles immobilized into the porous hydrochar for catalytic decomposition of phenol, *Appl. Catal. Environ.* 204 (2017) 566–576, <https://doi.org/10.1016/j.apcatb.2016.12.005>.
- [71] J. Yu, Z. Zhu, H. Zhang, T. Chen, Y. Qiu, Z. Xu, D. Yin, Efficient removal of several estrogens in water by Fe-hydrochar composite and related interactive effect mechanism of H₂O₂ and iron with persistent free radicals from hydrochar of pinewood, *Sci. Total Environ.* 658 (2019) 1013–1022, <https://doi.org/10.1016/j.scitotenv.2018.12.183>.
- [72] L. Dai, B. Wu, F. Tan, M. He, W. Wang, H. Qin, X. Tang, Q. Zhu, K. Pan, Q. Hu, Engineered hydrochar composites for phosphorus removal/recovery: lanthanum doped hydrochar prepared by hydrothermal carbonization of lanthanum pretreated rice straw, *Bioresour. Technol.* 161 (2014) 327–332, <https://doi.org/10.1016/j.biortech.2014.03.086>.
- [73] X.Q. Chen, B. Li, Y. Shen, J.Z. Guo, Facile synthesis of calcite-impregnated hydrochar with high sorption capacity for Cu(II) from aqueous solution, *ACS Omega* 4 (2019) 15022–15029, <https://doi.org/10.1021/acsomega.9b01805>.
- [74] Y. Xia, H. Liu, Y. Guo, Z. Liu, W. Jiao, Immobilization of heavy metals in contaminated soils by modified hydrochar: efficiency, risk assessment and potential mechanisms, *Sci. Total Environ.* 685 (2019) 1201–1208, <https://doi.org/10.1016/j.scitotenv.2019.06.288>.
- [75] J. Deng, X. Li, X. Wei, Y. Liu, J. Liang, B. Song, Y. Shao, W. Huang, Hybrid silicate-hydrochar composite for highly efficient removal of heavy metal and antibiotics: coadsorption and mechanism, *Chem. Eng. J.* 387 (2020), 124097, <https://doi.org/10.1016/j.cej.2020.124097>.
- [76] X. Dong, Y. Wang, M. Jia, Z. Niu, J. Cai, X. Yu, X. Ke, J. Yao, X. Zhang, Sustainable and scalable in-situ synthesis of hydrochar-wrapped Ti₃AlC₂-derived nanofibers as adsorbents to remove heavy metals, *Bioresour. Technol.* 282 (2019) 222–227, <https://doi.org/10.1016/j.biortech.2019.03.010>.
- [77] L.M. Wu, D.S. Tong, C.S. Li, S.F. Ji, C.X. Lin, H.M. Yang, Z.K. Zhong, C.Y. Xu, W. H. Yu, C.H. Zhou, Insight into formation of montmorillonite-hydrochar nanocomposite under hydrothermal conditions, *Appl. Clay Sci.* 119 (2016) 116–125, <https://doi.org/10.1016/j.clay.2015.06.015>.
- [78] Q. Ma, L. Cui, S. Zhou, Y. Li, W. Shi, S. Ai, Iron nanoparticles in situ encapsulated in lignin-derived hydrochar as an effective catalyst for phenol removal, *Environ. Sci. Pollut. Res.* 25 (2018) 20833–20840, <https://doi.org/10.1007/s11356-018-2285-7>.
- [79] X. Yu, S. Liu, G. Lin, Y. Yang, S. Zhang, H. Zhao, C. Zheng, X. Gao, Promotion effect of KOH surface etching on sucrose-based hydrochar for acetone adsorption, *Appl. Surf. Sci.* 496 (2019), 143617, <https://doi.org/10.1016/j.apsusc.2019.143617>.
- [80] M.A. Islam, M.J. Ahmed, W.A. Khanday, M. Asif, B.H. Hameed, Mesoporous activated carbon prepared from NaOH activation of rattan (*Lacosperma secundiflorum*) hydrochar for methylene blue removal, *Ecotoxicol. Environ. Saf.* 138 (2017) 279–285, <https://doi.org/10.1016/j.ecoenv.2017.01.010>.
- [81] K. Sun, J. Tang, Y. Gong, H. Zhang, Characterization of potassium hydroxide (KOH) modified hydrochars from different feedstocks for enhanced removal of heavy metals from water, *Environ. Sci. Pollut. Res.* 22 (2015) 16640–16651, <https://doi.org/10.1007/s11356-015-4849-0>.
- [82] T. Zhang, X. Wu, S.M. Shaheen, Q. Zhao, X. Liu, J. Rinklebe, H. Ren, Ammonium nitrogen recovery from digestate by hydrothermal pretreatment followed by activated hydrochar sorption, *Chem. Eng. J.* 379 (2020), 122254, <https://doi.org/10.1016/j.cej.2019.122254>.
- [83] L. Ding, B. Zou, Y. Li, H. Liu, Z. Wang, C. Zhao, Y. Su, Y. Guo, The production of hydrochar-based hierarchical porous carbons for use as electrochemical supercapacitor electrode materials, *Colloids Surf. A Physicochem. Eng. Asp.* 423 (2013) 104–111, <https://doi.org/10.1016/j.colsurfa.2013.02.003>.
- [84] M. Sevilla, A.B. Fuertes, A green approach to high-performance supercapacitor electrodes: the chemical activation of hydrochar with potassium bicarbonate, *ChemSusChem* 9 (2016) 1880–1888, <https://doi.org/10.1002/cssc.201600426>.
- [85] X. Yu, S. Liu, G. Lin, Y. Yang, S. Zhang, H. Zhao, C. Zheng, X. Gao, KOH-activated hydrochar with engineered porosity as sustainable adsorbent for volatile organic compounds, *Colloids Surf. A Physicochem. Eng. Asp.* 588 (2020), 124372, <https://doi.org/10.1016/j.colsurfa.2019.124372>.
- [86] G.G. Huang, Y.F. Liu, X.X. Wu, J.J. Cai, Activated carbons prepared by the KOH activation of a hydrochar from garlic peel and their CO₂ adsorption performance, *Xinjing Tan Cailiao/New Carbon Mater.* 34 (2019) 247–257, [https://doi.org/10.1016/S1872-5805\(19\)60014-4](https://doi.org/10.1016/S1872-5805(19)60014-4).
- [87] D.H. Nguyen, H.N. Tran, H.P. Chao, C.C. Lin, Effect of nitric acid oxidation on the surface of hydrochars to sorb methylene blue: an adsorption mechanism comparison, *Adsorpt. Sci. Technol.* 37 (2019) 607–622, <https://doi.org/10.1177/0263617419867519>.
- [88] Y. Xia, T. Yang, N. Zhu, D. Li, Z. Chen, Q. Lang, Z. Liu, W. Jiao, Enhanced adsorption of Pb(II) onto modified hydrochar: modeling and mechanism analysis, *Bioresour. Technol.* 288 (2019) 1–8, <https://doi.org/10.1016/j.biortech.2019.121593>.
- [89] Y. Xue, B. Gao, Y. Yao, M. Inyang, M. Zhang, A.R. Zimmerman, K.S. Ro, Hydrogen peroxide modification enhances the ability of biochar (hydrochar) produced from hydrothermal carbonization of peanut hull to remove aqueous heavy metals: batch and column tests, *Chem. Eng. J.* 200–202 (2012) 673–680, <https://doi.org/10.1016/j.cej.2012.06.116>.
- [90] F. Gao, G. Shao, J. Qu, S. Lv, Y. Li, M. Wu, Tailoring of porous and nitrogen-rich carbons derived from hydrochar for high-performance supercapacitor electrodes, *Electrochim. Acta* 155 (2015) 201–208, <https://doi.org/10.1016/j.electacta.2014.12.069>.
- [91] X. Zhu, Y. Liu, C. Zhou, S. Zhang, J. Chen, Novel and high-performance magnetic carbon composite prepared from waste hydrochar for dye removal, *ACS Sustain. Chem. Eng.* 2 (2014) 969–977, <https://doi.org/10.1021/sc400547y>.
- [92] Y. Liu, X. Zhu, F. Qian, S. Zhang, J. Chen, Magnetic activated carbon prepared from rice straw-derived hydrochar for triclosan removal, *RSC Adv.* 4 (2014) 63620–63626, <https://doi.org/10.1039/c4ra11815d>.
- [93] B. Li, Q. Wang, J.Z. Guo, W.W. Huan, L. Liu, Sorption of methyl orange from aqueous solution by protonated amine modified hydrochar, *Bioresour. Technol.* 268 (2018) 454–459, <https://doi.org/10.1016/j.biortech.2018.08.023>.
- [94] X. Zhu, Y. Liu, F. Qian, C. Zhou, S. Zhang, J. Chen, Preparation of magnetic porous carbon from waste hydrochar by simultaneous activation and magnetization for tetracycline removal, *Bioresour. Technol.* 154 (2014) 209–214, <https://doi.org/10.1016/j.biortech.2013.12.019>.
- [95] X. Zhu, Y. Liu, G. Luo, F. Qian, S. Zhang, J. Chen, Facile fabrication of magnetic carbon composites from hydrochar via simultaneous activation and magnetization for triclosan adsorption, *Environ. Sci. Technol.* 48 (2014) 5840–5848, <https://doi.org/10.1021/es500531c>.
- [96] Q. Ning, Y. Liu, S. Liu, L. Jiang, G. Zeng, Z. Zeng, X. Wang, J. Li, Z. Kare, Fabrication of hydrochar functionalized Fe-Mn binary oxide nanocomposites: characterization and 17 β -estradiol removal, *RSC Adv.* 7 (2017) 37122–37129, <https://doi.org/10.1039/c7ra06065c>.
- [97] Q. Chu, S. Xu, L. Xue, Y. Liu, Y. Feng, S. Yu, L. Yang, B. Xing, Bentonite hydrochar composites mitigate ammonia volatilization from paddy soil and improve nitrogen use efficiency, *Sci. Total Environ.* 718 (2020), 137301, <https://doi.org/10.1016/j.scitotenv.2020.137301>.
- [98] Y. Hua, X. Zheng, L. Xue, L. Han, S. He, T. Mishra, Y. Feng, L. Yang, B. Xing, Microbial aging of hydrochar as a way to increase cadmium ion adsorption capacity: process and mechanism, *Bioresour. Technol.* 300 (2020), 122708, <https://doi.org/10.1016/j.biortech.2019.122708>.
- [99] A.U. Rajapaksha, S.S. Chen, D.C.W. Tsang, M. Zhang, M. Vithanage, S. Mandal, B. Gao, N.S. Bolan, Y.S. Ok, Engineered/designer biochar for contaminant removal/immobilization from soil and water: potential and implication of biochar modification, *Chemosphere* 148 (2016) 276–291, <https://doi.org/10.1016/j.chemosphere.2016.01.043>.
- [100] Y. Shi, T. Zhang, H. Ren, A. Kruse, R. Cui, Polyethylene imine modified hydrochar adsorption for chromium (VI) and nickel (II) removal from aqueous solution, *Bioresour. Technol.* 247 (2018) 370–379, <https://doi.org/10.1016/j.biortech.2017.09.107>.
- [101] M. Minale, A. Guadie, Y. Liu, Y. Meng, X. Wang, J. Zhao, Insight into adsorption behavior of chlortetracycline and cadmium in aqueous solution using a novel manganese ferrite loaded swine manure hydrochar, *J. Environ. Chem. Eng.* 9 (2021), 106785, <https://doi.org/10.1016/j.jece.2021.106785>.
- [102] O.M. Rodríguez-Narvaéz, O. Serrano-Torres, K. Wrobel, E. Brillas, J.M. Peralta-Hernandez, Production of free radicals by the co₂p/Oxone system to carry out diclofenac degradation in aqueous medium, *Water Sci. Technol.* 78 (2018) 2131–2140, <https://doi.org/10.2166/wst.2018.489>.
- [103] O.M. Rodríguez-Narvaéz, J.M.J.M. Peralta-Hernandez, A. Goonetilleke, E.R.E. R. Bandala, Biochar-supported nanomaterials for environmental applications, *J. Ind. Eng. Chem.* 78 (2019) 21–33, <https://doi.org/10.1016/j.jiec.2019.06.008>.
- [104] L. Ding, Z. Wang, Y. Li, Y. Du, H. Liu, Y. Guo, A novel hydrochar and nickel composite for the electrochemical supercapacitor electrode material, *Mater. Lett.* 74 (2012) 111–114, <https://doi.org/10.1016/j.matlet.2012.01.070>.
- [105] S. Mortazavian, H. An, D. Chun, J. Moon, Activated carbon impregnated by zero-valent iron nanoparticles (AC/nZVI) optimized for simultaneous adsorption and reduction of aqueous hexavalent chromium: material characterizations and kinetic studies, *Chem. Eng. J.* 353 (2018) 781–795, <https://doi.org/10.1016/J.CEJ.2018.07.170>.
- [106] A.B. Zeidman, O.M. Rodríguez-Narvaéz, J. Moon, E.R. Bandala, Removal of antibiotics in aqueous phase using silica-based immobilized nanomaterials: a review, *Environ. Technol. Innov.* 20 (2020), 101030, <https://doi.org/10.1016/j.eti.2020.101030>.
- [107] S. Mortazavian, T. Jones-Lepp, J.H. Bae, D. Chun, E.R. Bandala, J. Moon, Heat-treated biochar impregnated with zero-valent iron nanoparticles for organic contaminants removal from aqueous phase: material characterizations and kinetic

- studies, *J. Ind. Eng. Chem.* 76 (2019) 197–214, <https://doi.org/10.1016/j.jiec.2019.03.041>.
- [108] S. Mortazavian, E.R. Bandala, J.H. Bae, D. Chun, J. Moon, Assessment of p-nitroso dimethylaniline (pNDA) suitability as a hydroxyl radical probe: investigating bleaching mechanism using immobilized zero-valent iron nanoparticles, *Chem. Eng. J.* 385 (2020), 123748, <https://doi.org/10.1016/j.cej.2019.123748>.
- [109] Z. Tang, Y. Deng, T. Luo, Y. sheng Xu, N. min Zhu, Enhanced removal of Pb(II) by supported nanoscale Ni/Fe on hydrochar derived from biogas residues, *Chem. Eng. J.* 292 (2016) 224–232, <https://doi.org/10.1016/j.cej.2016.01.113>.
- [110] L. Zhou, M. Cai, X. Zhang, N. Cui, G. Chen, G.Y. Zou, Key role of hydrochar in heterogeneous photocatalytic degradation of sulfamethoxazole using Ag3PO4-based photocatalysts, *RSC Adv.* 9 (2019) 35636–35645, <https://doi.org/10.1039/c9ra07843f>.
- [111] M.A. Khan, A.A. Alqadami, M. Otero, M.R. Siddiqui, Z.A. Alothman, I. Alsohaimi, M. Rafatullah, A.E. Hamedelniel, Heteroatom-doped magnetic hydrochar to remove post-transition and transition metals from water: synthesis, characterization, and adsorption studies, *Chemosphere* 218 (2019) 1089–1099, <https://doi.org/10.1016/j.chemosphere.2018.11.210>.
- [112] F.N. Çatıoğlu, S. Akay, B. Gözmen, E. Turunc, I. Anastopoulos, B. Kayan, D. Kalderis, Fe-modified hydrochar from orange peel as adsorbent of food colorant brilliant black: process optimization and kinetic studies, *Int. J. Environ. Sci. Technol.* (2019), <https://doi.org/10.1007/s13762-019-02593-z>.
- [113] S. Kannan, Y. Garipey, G.S.V. Raghavan, Optimization and characterization of hydrochar produced from microwave hydrothermal carbonization of fish waste, *Waste Manag.* 65 (2017) 159–168, <https://doi.org/10.1016/j.wasman.2017.04.016>.
- [114] L. Cao, I.K.M. Yu, D.W. Cho, D. Wang, D.C.W. Tsang, S. Zhang, S. Ding, L. Wang, Y.S. Ok, Microwave-assisted low-temperature hydrothermal treatment of red seaweed (*Gracilaria lemaneiformis*) for production of levulinic acid and algae hydrochar, *Bioresour. Technol.* 273 (2019) 251–258, <https://doi.org/10.1016/j.biortech.2018.11.013>.
- [115] L. Dai, C. He, Y. Wang, Y. Liu, Z. Yu, Y. Zhou, L. Fan, D. Duan, R. Ruan, Comparative study on microwave and conventional hydrothermal pretreatment of bamboo sawdust: hydrochar properties and its pyrolysis behaviors, *Energ. Convers. Manag.* 146 (2017) 1–7, <https://doi.org/10.1016/j.enconman.2017.05.007>.
- [116] Y. Shao, Y. Long, H. Wang, D. Liu, D. Shen, T. Chen, Hydrochar derived from green waste by microwave hydrothermal carbonization, *Renew. Energy* (2019) 1327–1334, <https://doi.org/10.1016/j.renene.2018.09.041>.
- [117] B. Li, J. Guo, K. Lv, J. Fan, Adsorption of methylene blue and Cd(II) onto maleylated modified hydrochar from water, *Environ. Pollut.* 254 (2019), 113014, <https://doi.org/10.1016/j.envpol.2019.113014>.
- [118] B. Li, J.Q. Lv, J.Z. Guo, S.Y. Fu, M. Guo, P. Yang, The polyaminocarboxylated modified hydrochar for efficient capturing methylene blue and Cu(II) from water, *Bioresour. Technol.* 275 (2019) 360–367, <https://doi.org/10.1016/j.biortech.2018.12.083>.
- [119] S. Ismadji, D.S. Tong, F.E. Soetaredjo, A. Ayucitra, W.H. Yu, C.H. Zhou, Bentonite hydrochar composite for removal of ammonium from Koi fish tank, *Appl. Clay Sci.* 119 (2016) 146–154, <https://doi.org/10.1016/j.clay.2015.08.022>.
- [120] H.N. Tran, S.J. You, H.P. Chao, Insight into adsorption mechanism of cationic dye onto agricultural residues-derived hydrochars: negligible role of π - π interaction, *Korean J. Chem. Eng.* 34 (2017) 1708–1720, <https://doi.org/10.1007/s11814-017-0056-7>.
- [121] H.N. Tran, S.J. You, T.V. Nguyen, H.P. Chao, Insight into the adsorption mechanism of cationic dye onto biosorbents derived from agricultural wastes, *Chem. Eng. Commun.* 204 (2017) 1020–1036, <https://doi.org/10.1080/00986445.2017.1336090>.
- [122] H.N. Tran, Y.F. Wang, S.J. You, H.P. Chao, Insights into the mechanism of cationic dye adsorption on activated charcoal: the importance of Π - Π interactions, *Process. Saf. Environ. Prot.* 107 (2017) 168–180, <https://doi.org/10.1016/j.psep.2017.02.010>.
- [123] X. Peng, Z. Yan, X. Cheng, Y. Li, A. Wang, L. Chen, Quaternary ammonium-functionalized rice straw hydrochar as efficient adsorbents for methyl orange removal from aqueous solution, *Clean Technol. Environ. Policy* 21 (2019) 1269–1279, <https://doi.org/10.1007/s10098-019-01703-2>.
- [124] A.M. Clurman, O.M. Rodríguez-Narvaez, A. Jayarathne, G. De Silva, M. I. Ranasinghe, A. Goonetilleke, E.R. Bandala, Influence of surface hydrophobicity/hydrophilicity of biochar on the removal of emerging contaminants, *Chem. Eng. J.* 402 (2020), 126277, <https://doi.org/10.1016/j.cej.2020.126277>.
- [125] V. Benavente, A. Fullana, N.D. Berge, Life cycle analysis of hydrothermal carbonization of olive mill waste: comparison with current management approaches, *J. Clean. Prod.* 142 (2017) 2637–2648, <https://doi.org/10.1016/j.jclepro.2016.11.013>.
- [126] K. Meisel, A. Clemens, C. Fühner, M. Breulmann, S. Majer, D. Thrän, Comparative life cycle assessment of HTC concepts valorizing sewage sludge for energetic and agricultural use, *Energies* 12 (2019), <https://doi.org/10.3390/en12050786>.
- [127] M. Owsianiak, M.W. Ryberg, M. Renz, M. Hitzl, M.Z. Hauschild, Environmental performance of hydrothermal carbonization of four wet biomass waste streams at industry-relevant scales, *ACS Sustain. Chem. Eng.* 4 (2016) 6783–6791, <https://doi.org/10.1021/acssuschemeng.6b01732>.
- [128] A. Mohammadi, G. Venkatesh, M. Sandberg, S. Eskandari, S. Joseph, K. Granström, A comprehensive environmental life cycle assessment of the use of hydrochar pellets in combined heat and power plants, *Sustain* 12 (2020) 1–15, <https://doi.org/10.3390/su12219026>.
- [129] N.D. Berge, L. Li, J.R.V. Flora, K.S. Ro, Assessing the environmental impact of energy production from hydrochar generated via hydrothermal carbonization of food wastes, *Waste Manag.* 43 (2015) 203–217, <https://doi.org/10.1016/j.wasman.2015.04.029>.
- [130] J. Zhang, G. Li, A. Borrión, Life cycle assessment of electricity generation from sugarcane bagasse hydrochar produced by microwave assisted hydrothermal carbonization, *J. Clean. Prod.* 291 (2021), 125980, <https://doi.org/10.1016/j.jclepro.2021.125980>.
- [131] G. Sztancs, A. Kovacs, A.J. Toth, P. Mizsey, P. Billen, D. Fozer, Catalytic hydrothermal carbonization of microalgae biomass for low-carbon emission power generation: the environmental impacts of hydrochar co-firing, *Fuel* 300 (2021), 120927, <https://doi.org/10.1016/j.fuel.2021.120927>.
- [132] F. Gievers, A. Loewen, M. Nelles, Hydrothermal Carbonization (HTC) of Sewage Sludge: GHG Emissions of Various Hydrochar Applications, Springer International Publishing, 2019, https://doi.org/10.1007/978-3-319-92237-9_7.
- [133] R. Mahmood, G.K. Parshetti, R. Balasubramanian, Energy, exergy and techno-economic analyses of hydrothermal oxidation of food waste to produce hydrochar and bio-oil, *Energy* 102 (2016) 187–198, <https://doi.org/10.1016/j.energy.2016.02.042>.
- [134] B. Mendecka, L. Lombardi, F. Micali, A. De Risi, Energy recovery from olive pomace by hydrothermal carbonization on hypothetical industrial scale: a LCA perspective, *Waste Biomass Valoriz.* 11 (2020) 5503–5519, <https://doi.org/10.1007/s12649-020-01212-0>.
- [135] G. Contreras-Zarazúa, M. Martín, J.M. Ponce-Ortega, J.G. Segovia-Hernández, Sustainable design of an optimal supply chain for furfural production from agricultural wastes, *Ind. Eng. Chem. Res.* 60 (2021) 14495–14510, <https://doi.org/10.1021/acs.iecr.1c01847>.
- [136] Scientific Applications International Corporation (SAIC), LIFE CYCLE ASSESSMENT: PRINCIPLES AND PRACTICE, 2006.
- [137] M. Cavali, N. Libardi Junior, J.D. de Sena, A.L. Woiciechowski, C.R. Soccol, P. Belli Filho, R. Bayard, H. Benbelkacem, A.B. de Castilhos Junior, A review on hydrothermal carbonization of potential biomass wastes, characterization and environmental applications of hydrochar, and biorefinery perspectives of the process, *Sci. Total Environ.* 857 (2023), 159627, <https://doi.org/10.1016/j.scitotenv.2022.159627>.
- [138] A. Kumar, K. Saini, T. Bhaskar, Hydrochar and biochar: production, physicochemical properties and techno-economic analysis, *Bioresour. Technol.* 310 (2020), 123442, <https://doi.org/10.1016/j.biortech.2020.123442>.
- [139] E. Medina-Martos, I.R. Istrate, J.A. Villamil, J.L. Gálvez-Martos, J. Dufour, Á. F. Mohedano, Techno-economic and life cycle assessment of an integrated hydrothermal carbonization system for sewage sludge, *J. Clean. Prod.* 277 (2020), <https://doi.org/10.1016/j.jclepro.2020.122930>.
- [140] P. Roy, A. Dutta, J. Gallant, Evaluation of the life cycle of hydrothermally carbonized biomass for energy and horticulture application, *Renew. Sustain. Energy Rev.* 132 (2020), 110046, <https://doi.org/10.1016/j.rser.2020.110046>.
- [141] V. Mau, A. Gross, Energy conversion and gas emissions from production and combustion of poultry-litter-derived hydrochar and biochar, *Appl. Energy* 213 (2018) 510–519, <https://doi.org/10.1016/j.apenergy.2017.11.033>.